

## TEST REPORT


<b>Report Ref.:</b>	LEI17070401A Original		
<b>Date Received:</b>	04/07/2017	<b>Date Issued:</b>	07/07/2017

<b>Company Name &amp; Address:</b>	Camira Fabrics Limited CAMIRA FABRICS LIMITED , HD9 4AY
<b>Contact Name:</b>	Rebecca Grimes

<b>Order Number:</b>	6342
<b>Sample Description:</b>	Wool Rich Moquette - Face To Face - With Crinkle
<b>Colour:</b>	CCNC14
<b>Quality:</b>	Aura - Wool Rich Moquette Face To Face - With Crinkle Q64 & Q176
<b>Batch Number:</b>	344964
<b>End Use:</b>	Transport Upholstery
<b>Retailer:</b>	EN14465

Test	Method	Sample	Result
Martindale Abrasion Resistance - 12 kPa	BS EN 14465: 2003 Annex A		See Results

Tests marked (^) in this report have been performed by an approved 3rd party laboratory.  
Tests marked (\*) in this report are not included in our UKAS scope of accreditation.

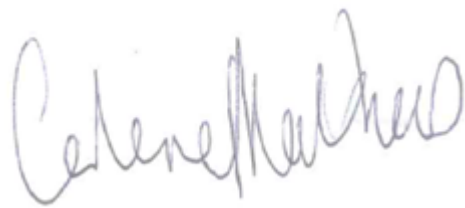

Carlene Matthews  
(Jobsheet Technician)

**Martindale Abrasion Resistance - 12 kPa BS EN 14465: 2003 Annex A**  
**Conditioning Parameters: 20°C±2°C & 65% rH±4% rH**

Fabric Type	Cut pile			
Test load: 12 kPa				
Specimen 1 - Shade Change @ 3000 & 5000 revs	4 - 5			
	Result*	Performance level		
Head 1	No fabric breakdown @ 100,000 Revs	A = 45,000		
Head 2	No fabric breakdown @ 100,000 Revs	B = 25,000 - 40,000		
Head 3	No fabric breakdown @ 100,000 Revs	C = 10,000 - 20,000		
Overall result (Lowest individual result)	100,000 Revs			
Overall performance level	A			
*Inspection interval before the end-point was reached.				
BS 2543: 2004 Classification (Minimum levels for customer reference)				
	Flat woven	Figured weave	Woven/Flocked/Non-Woven Pile Fabrics	Knitted
Light Domestic	B - 15,000	B - 12,000	B - 15,000	B - 15,000
General Domestic	B - 20,000	B - 15,000	B - 20,000	B - 20,000
Heavy Domestic	B - 25,000	B - 20,000	B - 25,000	B - 25,000
General Contract	B - 30,000	B - 30,000	B - 25,000	B - 25,000
Severe Contract	A - 40,000	A - 40,000	A - 30,000	A - 30,000

Overall Test Result: See Results  
Uncertainty: ±17%

*This report is made solely on the basis of your instructions and/or information and materials supplied by you. It is not intended to be a recommendation for any particular course of action. Intertek does not accept a duty of care or any other responsibility to any person other than the Client in respect of this report and only accepts liability to the Client insofar as is expressly contained in the terms and conditions governing Intertek's provision of services to you. Intertek makes no warranties or representations either express or implied with respect to this report save as provided for in those terms and conditions. We have aimed to conduct the Review on a diligent and careful basis and we do not accept any liability to you for any loss arising out of or in connection with this report, in contract, tort, by statute or otherwise, except in the event of our gross negligence or willful misconduct.*

*The reported expanded uncertainty is based on a standard uncertainty multiplied by a coverage factor of  $k = 2$ , providing a level of confidence of approximately 95%. Any Pass/Fail statements do not take into account the Measurement of Uncertainty. The Uncertainty budgets are stated for each Test method, these are for reference, and should be considered when results are close to Specification Limits / Requirements.*